

MLR 69 1

Iowa State Highway Commission
Materials Department
Special Investigations

Research Project R-229
Final Report

LIGHTWEIGHT
AGGREGATE
use in
Structural
Concrete

APRIL 9, 1969

Table of Contents

| <u>Item</u> | | <u>Page</u> |
|-------------|---------------------------|-------------|
| | Acknowledgement | |
| 1.0 | Introduction | 1 |
| 2.0 | Purpose | 1 |
| 3.0 | Materials | 1 |
| 4.0 | Laboratory Procedure | 4 |
| 5.0 | Interpretation of Results | 7 |
| 6.0 | Summary | 9 |
| 7.0 | Appendix | 11 |

ACKNOWLEDGEMENT -

We wish to express our appreciation to Mr. J. H. Boemler and Prestressed Concrete of Iowa, Inc., Iowa Falls, for their cooperation on this project.

We also wish to thank Mr. John Lane, Portland Cement Concrete Engineer, and Mr. Bernard C. Brown, Testing Engineer, for their direction and assistance in this project.

LIGHTWEIGHT AGGREGATE USE IN STRUCTURAL CONCRETE

1.0 INTRODUCTION

The Iowa State Highway Commission has adopted a number of rigid safety requirements that the Bureau of Public Roads has set forth as standards for road construction. One of these safety requirements is the elimination of two piers on Interstate grade separations, thus leaving two long spans. These longer spans lower the ability of prestressed concrete beams to compete economically with steel beams. In an effort to be more competitive, the prestressing companies have been studying the use of lightweight aggregate in structural concrete.

2.0 PURPOSE

The purpose of this project is to determine which of the three lightweight aggregates proposed for use by Prestressed Concrete of Iowa, Inc., Iowa Falls, will produce concrete with sufficient strength and durability to be used by the Iowa State Highway Commission for structural concrete. The effects of curing on the structural concrete will also be studied.

3.0 MATERIALS

Three lightweight aggregates were used in this study. They were:

HAYDITE

Source: Carter-Waters Corporation, Centerville, Iowa

Lab. Nos. AAG7-247, AAG7-371*, AAG7-302*, AAG7-273, AAG7-266

| | | | |
|--------------------------------------|-------|-------|-----|
| Sp. Gr. (S.S.D.) | 1.876 | 1.905 | |
| % Abs. (S.S.D.) | 8.85 | 7.20 | |
| % Loss Method "A" Freeze and Thaw | 2.9 | | 1.7 |
| % Wear, LA Abrasion, Grading C | 22 | | 25 |
| Unit Weight (Lb/Cu.Ft.) | | | |
| +4 | 55.1 | 57.69 | |
| -4 | | 53.38 | |
| MIX | | 55.07 | |

| Gradation | % Passing | % Passing |
|-----------|-----------|-----------|
| 3/8" | 100 | 100 |
| #4 | 55 | 59 |
| #8 | 8.5 | 3.8 |

*No aggregate tests were performed on these samples, but since they were from the same source, it is assumed that they would produce similar results.

IDEALITE

Source: The Idealite Company, 821 Seventeenth Street, Denver, Colorado

Lab. No. AAG7-314

| | |
|------------------------------------|-------|
| Sp. Gr. (S.S.D.) | 1.627 |
| % Abs. (S.D.D.) | 7.73 |
| % Loss Method "A" Freeze & Thaw | 2.8 |
| % Wear, LA Abrasion Grading B | 22 |
| Unit Weight (Lb/Cu.Ft.) | 55.37 |

| Gradation | Blend Grading % Passing | Med. Grading % Passing |
|-----------|----------------------------|---------------------------|
| 1" | 100 | - |
| 3/4" | 99 | - |
| 1/2" | 81 | - |
| 3/8" | 42 | 100 |
| #4 | 14 | 62 |
| #8 | 4.0 | 12 |

MATERIALITE

Source: Material Service, Division of General Dynamics Corporation
300 W. Washington Street, Chicago, Illinois

| | |
|-------------------------|----------|
| Lab. No. | AAG7-355 |
| Sp. Gr. (S.S.D.) | 1.580 |
| % Abs. (S.D.D.) | 8.3 |
| % Loss Method "A" | |
| Freeze & Thaw | 3.1 |
| % Wear, LA Abrasion | |
| Grading B | 29 |
| Unit Weight (Lb/Cu.Ft.) | 52.89 |

| Gradation | % Passing |
|-----------|-----------|
| 3/4" | 100 |
| 1/2" | 91 |
| 3/8" | 38 |
| #4 | 2.0 |

The Fine Aggregate used for Lab. Mixes (AAS7-41) was from Hallett's Pit at Ames complying with Section 4110 of the Standard Specifications. It had the following gradation:

| Sieve Size | % Passing |
|------------|-----------|
| 3/8" | 100 |
| #4 | 99+ |
| #8 | 94 |
| #16 | 70 |
| #30 | 35 |
| #50 | 8.2 |
| #100 | 0.8 |
| #200 | 0.4 |

For the Plant Mixed concrete, fine aggregate from Welden Brothers in Iowa Falls was used.

Pozzolith 100R, a product of the Master Builders Company, 2490 Lee Boulevard, Cleveland, Ohio, was used as an additive to yield more desirable characteristics with respect to strength and workability. Lot Nos. P-477-G7 and P-310-E7 as tested under Lab. Nos. AAM7-36 and AAM7-21 respectively, were used in this project, with little variation between the two lots.

Two blends of R-11 cement (AC6-2344 and AC7-5637) were used in making the mixtures. An R-11 blend is composed of 7 different brands of Type I cement mixed together in equal proportions. There was no appreciable difference in the two blends, therefore it can be assumed that the cement in the mixtures did not affect the results.

4.0 LABORATORY PROCEDURE

It was originally planned that the concrete would be batched, mixed and cured for the first day at the prestress plant. After curing by steam, radiant heat or simply by being covered with plastic, the concrete beams and cylinders would then be transported to the laboratory and removed from the molds.

Nine beams and cylinders were made at the prestress plant using saturated Haydite Lightweight Aggregate. The following proportions were used for 1 cu.yd.:

| | |
|--|----------------------------------|
| Cement | 700 lb. |
| Sand | 1324 lb. (S.S.D.) |
| Haydite | 850 lb.* |
| Pozzolith 100R = | 21 oz. (3 oz./100 lb. of cement) |
| Water necessary for desired consistency. | |
| Desirable slump = | 2 1/2 - 3 in. max. |

Sets of three beams and three cylinders were cured by each of the methods available. Durability factors were determined per ASTM-C-291 with the following exceptions:

- (1) The beams were 18" long.
- (2) Their locations in the freezer were unchanged.
- (3) One end of the beam was placed toward the bottom of the freezer for the entire test.
- (4) The beams were normally read at 56 cycle intervals.

The compressive strength of the cylinders was computed per ASTM C-39.

The modulus of elasticity was determined at the same time as the cylinders were tested to failure in compression.

*The Haydite in this plant mix was on an "as found" basis, and no correction was made for moisture content.

The cylinders were not moist for testing. Two lines were drawn around the cylinders two inches from each end (8 inches apart). The mechanical strain jacket was then positioned around the cylinder. The three set screws on the upper ring of the strain jacket were positioned on the upper line and adjusted so the jacket was not rubbing on the cylinder. The two set screws at the base were positioned on the line. One side of the strain jacket was held at 8 inches with a fixed rod that was spring loaded so all movement was measured on the other side by one dial. The resulting stress and strain were plotted on a graph and the slope of a straight line through the points from no stress to the stress representing $0.4 f_c$ was determined to be the modulus of elasticity.

Because of the inconvenience caused by making the beams at the plant and then transporting them to Ames, it was decided to do the balance of the work at the Ames Laboratory.

In the laboratory, eleven batches of concrete were mixed. The following proportions were used for 1 cu. yd.:

HAYDITE MIX

| | |
|---------------------------------|--|
| Mix Numbers | 6-9 |
| Lightweight Aggregate Condition | Mix No's. 6-7 Saturated 8-9 Air Dry |
| Cement | 709 lbs. |
| Sand | 1341 lbs. (S.S.D.) |
| Haydite | 861 lbs. (Oven dry basis) |
| Pozzolith (100R) | 21.3 oz. |

| Haydite Gradation | Sieve Size | % Passing |
|-------------------|------------|-----------|
| | 3/8" | 100 |
| | #4 | 36 |
| | #8 | 1.4 |

IDEALITE MIX

| | | |
|---------------------------------|------------------------------------|------------------------------|
| Mix Numbers | 10-13 | 14 |
| Lightweight Aggregate Condition | 10, 11 Saturated 12, 13 Air Dry | Air Dry |
| Cement | 747 lb. | 761 lb. |
| Sand | 1140 lb. (S.S.D.) | 1162 lb. |
| Idealite | 934 lb. | 952 lb. |
| Pozzolith (100R) | (Oven dry basis) 22.4 oz. | (Oven dry basis) 22.8 oz. |

| Idealite Gradation | Sieve Size | % Passing | % Passing |
|--------------------|------------|-----------|-----------|
| | 3/4" | 100 | - |
| | 1/2" | 91 | - |
| | 3/8" | 71 | 100 |
| | #4 | 38 | 36 |
| | #8 | 8 | 1.4 |

MATERIALITE MIX

| | |
|---------------------------------|----------------------------|
| Mix Numbers | 15-16 |
| Lightweight Aggregate Condition | 15 Saturated 16 Air Dry |
| Cement | 701 lb. |
| Sand | 1143 lb. |
| Materialite | 920 lb. (Oven dry basis) |
| Pozzolith (100R) | 21.0 oz. |

| Materialite Gradation | Sieve Size | % Passing |
|-----------------------|------------|-----------|
| | 3/4" | 100 |
| | 1/2" | 94 |
| | 3/8" | 39 |
| | #4 | 2.0 |

Three to six cylinders and three beams were made from each mix. The beams were cured as specified in the Bureau of Public Roads, "Interim Report on Concrete Prepared with Lightweight Aggregate" (September 27, 1962). This consisted of moist room curing (ASTM C-511) for 7 days, 50% relative humidity at 73°F. for 14 days, and 7 more days of moist curing. At the age of 28 days the beams were subjected to rapid freezing in air and thawing in water (ASTM C-291).

The cylinders (plant and laboratory mixed) were cured according to ASTM C-330 (moist cured to age of 7 days then 50% relative humidity and 73°F. until testing at 28 days).

5.0 INTERPRETATION OF RESULTS

The following durability factors were obtained for the plant mixed specimens: Radiant heat cure - 9, Covered with plastic - 11, Steam cure - 8. These durability factors were not acceptable.

Strengths obtained at 28 days were as follows: Radiant heat cure - 7265, Covered with plastic - 7525, Steam cure - 7445. The 28 day strength values were acceptable, but because of the durability factors the results could not be used to make valid conclusions.

A modulus of elasticity was determined for one of the plant mixed cylinders. The value obtained was 3.25×10^6 psi.

Table 1 is a summary of the results obtained with the plant mixed specimens.

The specimens mixed in the Laboratory (Table 2) were tested for compressive strength at 7 and 28 days. The Haydite mixes had strengths at 7 days from 4900 - 5130 psi. Seven day strengths for the Idealite mixtures ranged from 5370 - 6370 psi. No strength tests were run on the Materialite cylinders at 7 days.

Cylinders from Haydite mixes No. 7 and 8 were tested at 28 days with strengths of 6835 and 6720 psi being determined respectively. Idealite cylinders from mixes 11, 12 and 14 had 28 day strengths of 7250, 7580 and 7970 (27 day) psi respectively. Strengths obtained for the Materialite mixes Numbers 15 and 16 were 6685 and 6460 psi respectively. All strengths obtained were acceptable.

The following values for the modulus of elasticity were obtained:

| <u>Mix No.</u> | <u>Lightweight Aggregate</u> | <u>7 Day (psi)</u> | <u>28 Day (psi)</u> |
|----------------|------------------------------|------------------------|---------------------------------|
| 6 | Haydite | 2.86 x 10 ⁶ | - - - - |
| 7 | Haydite | - - - - | 3.58 x 10 ⁶ |
| 8 | Haydite | 2.92 x 10 ⁶ | 3.54 x 10 ⁶ |
| 11 | Idealite | - - - - | 3.20 x 10 ⁶ |
| 12 | Idealite | - - - - | 3.44 x 10 ⁶ |
| 14 (Finer) | Idealite | - - - - | 3.43 x 10 ⁶ (27 day) |
| 15 | Materialite | | 3.27 x 10 ⁶ |
| 16 | Materialite | | 3.34 x 10 ⁶ |

Durability factors were obtained for beams from all but one mix. Because of some of the beams crumbling, it was hard to determine a precise value. Durability factors for beams of the various mixes were as follows:

- 6 (Haydite) 2 @ 27, 1 @ 100
- 7 (Haydite) 2 @ 22, 1 @ 100
- 8 (Haydite) - 100
- 9 (Haydite) - 100
- 10 (Idealite) - 7
- 11 (Idealite) - 5
- 12 (Idealite) - 97
- 13 (Idealite) - 97
- 14 (Idealite) - None Determined
- 15 (Materialite) - 5
- 16 (Materialite) - 2 Beams @ 16, 1 @ 24

The results obtained for durability factors indicate that the condition of the aggregate for mixing has a direct effect on the durability. Those mixes with saturated aggregate for mixing (Mix No's. 6,7,10,11 and 15) all had very poor durability factors.

The condition of the beams after freeze and thaw was also used as an indication of the durability of the concretes. Figures 1 - 9 show the beams after testing. The only beams not pictured were those from Mix 11. They were badly cracked after 24 cycles in the freeze and thaw machine.

The beams made with air dry Idealite (Fig. 5, 6) had the least external deterioration after freeze and thaw. The beams made from air dry Materialite look good (Fig. 8) but were only tested for 27 cycles. They had durability factors of 5 and 19, much too low for acceptance.

Table 2 is a summary of the results for the laboratory mixed specimens.

6.0 SUMMARY

Sufficient strengths were obtained for all mixes. Only two types of mixes produced beams with durability factors acceptable for this study - the mixes made with air dry Haydite and air dry Idealite.

The effects of curing on plant mixed specimens were inconclusive because the mixes were made with saturated aggregate and the durability factors obtained from these mixes were too low to have much significance.

In order to produce concrete with acceptable durability, it is necessary to use air dried aggregate when mixing. This is a conclusion that can be drawn from this study. The Standard Specification 2403.04 (Paragraph A) states that "coarse aggregate shall be kept continuously and thoroughly wet for at least 48 hours before being used in the concrete". ACI Standards 1965 (ACI 614-59) states that the aggregate should be damp and implies that thoroughly wet aggregate will not give concrete with acceptable durability. The Standard Specifications were wrong and have been changed by Specification 624, "Special Provisions for Lightweight Concrete Bridge Units".

The Idealite was chosen for use by Prestressed Concrete of Iowa, Inc. because it had good durability and the least external deterioration after freeze and thaw. Although the Haydite had good durabilities, it was not selected because the ends of beams made with it crumbled badly during freeze and thaw cycles. The Materialite durabilities were too low for consideration.

7.0 APPENDIX

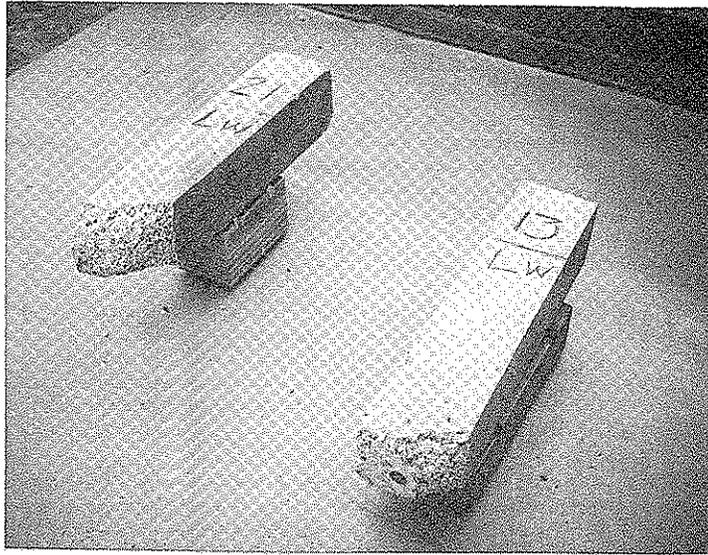


Figure 1 - Beams 13, 21 - Made with Saturated Haydite

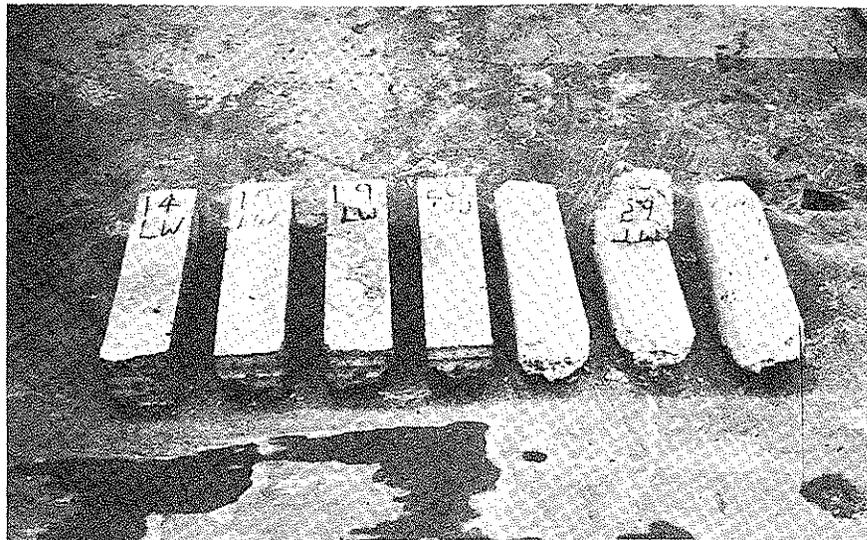


Figure 2 - Beams 14, 15, 19, 20 - Made with Saturated Haydite
Beams 28, 29, 30 - Made with Saturated Idealite



Figure 3 - Beams 16,17,18 - Made with
Air Dry Haydite

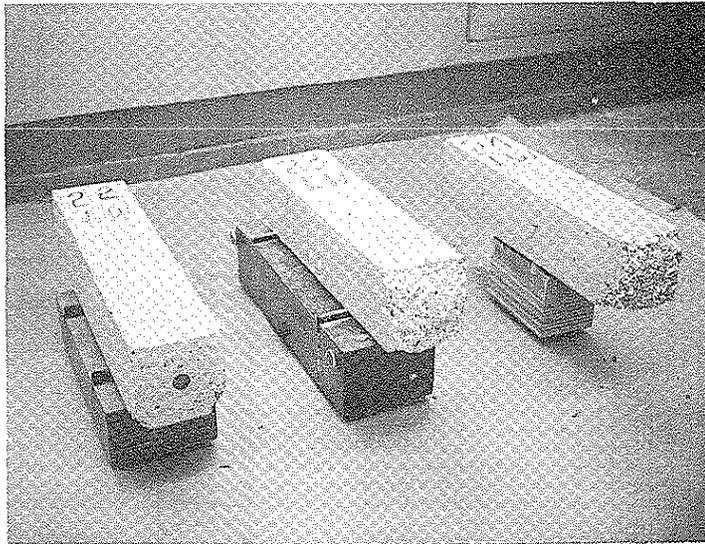


Figure 4 - Beams 22, 23, 24 - Made with
Air Dry Haydite

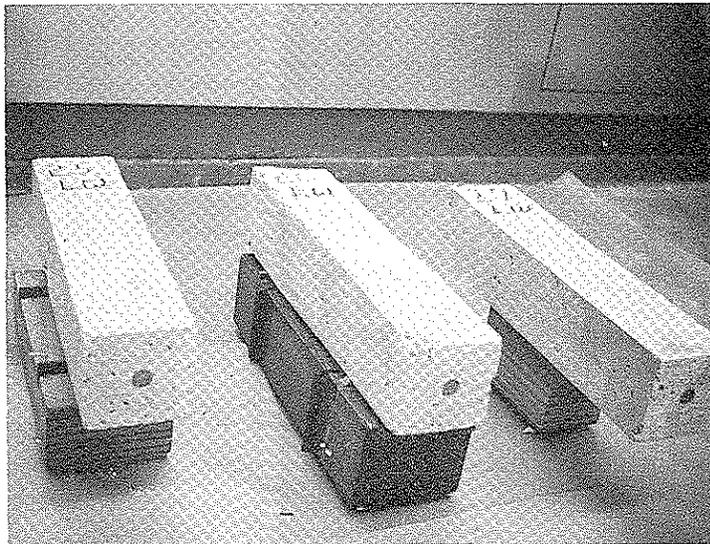


Figure 5 - Beams 25, 26, 27 - Made with Air Dry Idealite

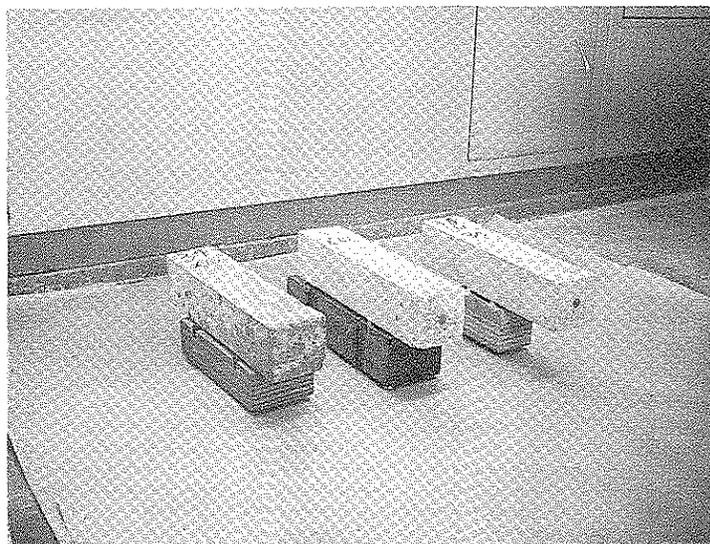


Figure 6 - Beams 34, 35, 36 - Made with Air Dry Idealite



Figure 7 - Beams 37, 38, 39 - Made with
Finer Air Dry Idealite

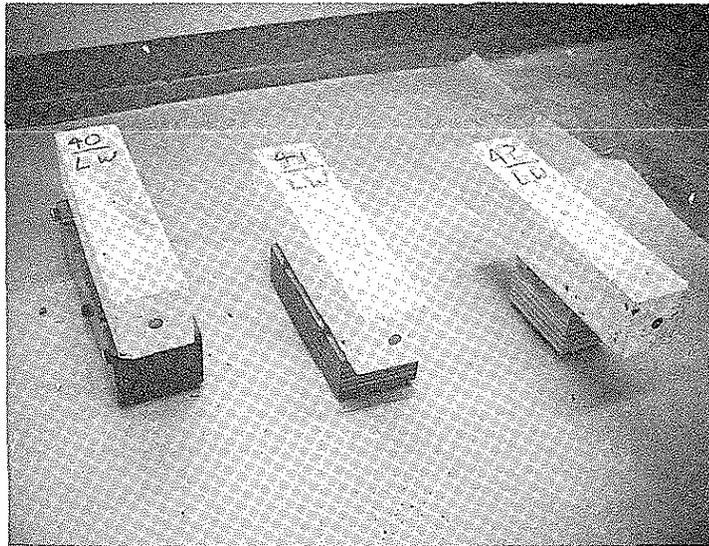


Figure 8 - Beams 40, 41, 42 - Made with
Air Dry Materialite
(DF = 2 @ 16, 1 @ 24)

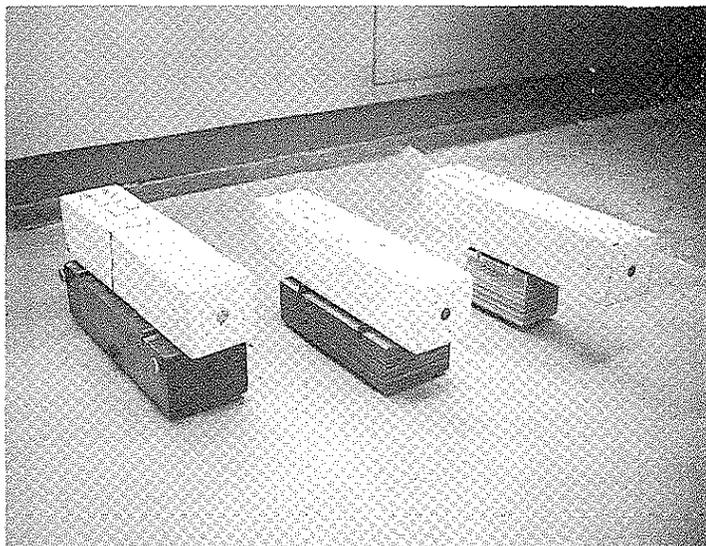


Figure 9 - Beams 43, 44, 45 - Made with Saturated Materialite (DF = 5)

Table 1

MATERIALS DEPARTMENT
DATA SHEET

Lightweight Aggregate (Haydite)
Plant Mixed Specimens

| Mix No. | 1 | 2 | 3 | 4 | 5 |
|---|---|-------------------------------|------------------------------------|---------------------|-----------------------------|
| Cylinder No. | 1-LW, 2-LW, 3-LW | 4-LW, 5-LW, 6-LW | 7-LW, 8-LW, 9-LW | | 1-A, 3-A, 5-A, 6-A |
| Condition at Mixing | Wet | Wet | Wet | Wet | Damp |
| Compressive Strength 28 day | 7265 | 7525 | 7445 | | |
| 43 day | | | | | 1-A, 3-A=6410 |
| Splitting Tensile Strength 43 day | | | | | 5-A, 6-A= 382 |
| Density, Lb./Cu.Ft. | | | | | |
| Absorption | | | 7-LW = 7.3 8-LW = 9.1 | | |
| Date Made | 8-10-67 | 8-10-67 | 8-14-67 | 8-14-67 | |
| Initial Cure | Radiant Heat 13-14 Hr. @ 165-170°F. | Covered by Tarp for 14 Hr. | Steam Cure 15 Hr. 140-150°F. | | |
| Modulus of Elasticity, (Tested Dry) 43 day | | | | | 3.25 x 10 ⁶ psi. |
| Beam Nos. | 1-LW, 2-LW, 3-LW | 4-LW, 5-LW, 6-LW | 7-LW, 8-LW, 9-LW | 10-LW, 11-LW, 12-LW | |
| Durability Factor Cycles | 9 45 | 11 56 | 8 39 | | |
| Growth, Inches - Cycles | .096 - 64 | .161 - 88 | .066 - 56 | | |
| Beam Condition | | | | | |

Table 2

MATERIALS DEPARTMENT
DATA SHEET

Lightweight Aggregate and Lightweight Concrete

| Mix No. | 6 | 7 | 8 | 9 | 10 | 11 | 12 | 13 | 14 | 15 | 16 |
|--------------------------------------|--------------------------|----------------------|--|-------------------------|--------------------|----------------------|----------------------|--------------------|-----------------------------|----------------------|--------------------------|
| Cylinder Nos. | 4551- 4555 | 4561- 4565 | 4556- 4560 | 4566- 4570 | 4577- 4582 | 4583- 4588 | 4571- 4576 | 4589- 4594 | 4595- 4600 | 4610- 4612 | 4607- 4609 |
| Lightweight Agg. | Haydite | Haydite | Haydite | Haydite | Idealite | Idealite | Idealite | Idealite | Idealite (finer) | Materialite | Materialite |
| Condition for mixing | Saturated | Saturated | Air dry | Air dry | Saturated | Saturated | Air dry | Air dry | Air dry | Saturated | Air dry |
| Cement Sacks/yd. | 7.49 | 7.59 | 7.58 | 7.49 | 7.93 | 8.05 | 7.92 | 7.90 | 8.10 | 7.25 | 7.66 |
| Slump | 2 1/2 | 3.0 | 2 3/4 | 2 1/2 | 3.0 | 3 1/2 | 3.0 | 2 1/2 | 2 1/2 | 4 1/2 | 4 1/2 |
| Compressive Str. 7 day 28 day | 4900 | 5130 6835 | 4910 6720 | 4985 | 5620 | 5370 7250 | 5935 7580 | 5845 | 6370 7970* | 6685 | 6460 |
| Splitting Tensile Str. 28 day | 437 | | | 383 | 398 | | | 367 | | | |
| Mod of Elasticity 7 day 28 day | 2.86x10 ⁶ | 3.58x10 ⁶ | 2.92x10 ⁶ 3.54x10 ⁶ | | | 3.20x10 ⁶ | 3.44x10 ⁶ | | 3.43x10 ⁶ | 3.27x10 ⁶ | 3.34x10 ⁶ |
| Concrete Abs. | | 6.76 | 7.58 | | | 6.99 | 6.11 | | 7.58 | 6.6 | 9.25 |
| Beam Nos. | <u>13-15</u> LW | <u>19-21</u> LW | <u>16-18</u> LW | <u>22-24</u> LW | <u>28-30</u> LW | <u>31-33</u> LW | <u>25-27</u> LW | <u>34-36</u> LW | <u>37-39</u> LW | <u>43-45</u> LW | <u>40-42</u> LW |
| Durability Factor | 2 @ 27 1 @ 100 | 2 @ 22 1 @ 100 | 100 | 100 | 7 | 5 | 97 | 97 | | 5 | 2 @ 16 1 @ 24 |
| Cycles | 133 321 | 110 316 | 321 | 305 | 36 | 24 | 312 | 308 | 2-209 1-241 | 27 | 78 121 |
| Growth (No.-Growth-Cycles) Inches | 2-.067-159 1-.052-321 | 2-.100-143 | .045-321 | .045-305 | .215-78 | .056-31 | .004-312 | .005-308 | 3-.066-185 | .046-38 | 2-.041-105 1-.040-129 |
| Beam Condition | Bottom end crumbling | ends crumbled | Bottom end crumbling | Bottom end crumbling | Disint- egrated | Badly cracked | very good | very good | top & bottom crumbled | | |
| Aggregate Abs. | 8.85 | 7.20 | | | 7.73 | | | | | 8.3 | |
| "A" F & T LA Abrasion | 2.9, 1.7 (C)22,25 | | | | 2.8 (B)22 | | | | | 3.1 (B)29 | |

* 27 day